

## Photocatalytic Degradation of Brown CGG Dye using Chemically Synthesized ZnO Nanoparticles

A.S.M. Asfaque Islam, Taslima Ferdous and Ajoy Kumar Das

Department of Applied Chemistry and Chemical Engineering, University of Dhaka, Dhaka 1000, Bangladesh

E-mail: taslima\_ferdous@yahoo.com

Received on 09. 04. 2014. Accepted for publication on 14.07. 2014.

### Abstract

The sunlight irradiated photocatalytic degradation of Brown CGG dye was studied using ZnO nanoparticle. The ZnO nanoparticle was prepared by a simple chemical method using  $Zn(NO_3)_2 \cdot 6H_2O$  and NaOH under optimum reaction conditions and the prepared nanoparticle was characterized by UV-visible spectroscopy, X-ray diffraction (XRD), Fourier transform infrared spectroscopy (FT-IR), energy dispersion X-ray spectroscopy (EDX) and scanning electron microscopy (SEM). The results of this investigation revealed that in the presence of sunlight, catalyst load of  $0.5 \text{ g} \cdot \text{L}^{-1}$  and time of contact of 40 min, ZnO nanoparticle showed substantial capability of removing Brown CGG dye from solution. An actual leather effluent containing Brown CGG as a major constituent along with other dyes and dyeing auxiliaries was treated using ZnO and the reduction in the chemical oxygen demand (COD) of the treated effluent revealed almost complete destruction of the organic molecules along with color removal.

**Keywords :** ZnO Nanoparticle, Photodegradation, Brown CGG.

### 1. Introduction

There are more than 100,000 commercially available dyes and globally over  $7 \times 10^5$  tons of dye is produced in a year and 15% of which is lost during the dyeing process [1]. Dyes can easily contaminate the water bodies through their discharge from the industries. Non-biodegradable nature of most of the dyes which result in perturbation in aquatic diversity by blocking the passage of sunlight through the water represents serious problems to the environment. It is reported that less than 1 ppm of dye content causes obvious water coloration [2]. Leather processing and leather products manufacturing are important export-orientated industries in Bangladesh. The full flourishing of this sector is significant for the country's economy. Most of these processing plants have no effluent treatment plant. They directly dispose untreated colored and toxic effluent into the nearby rivers and other waterways, thereby causing serious environmental pollution.

Development of technological systems for the removal of organic dyes has recently been on the rise. These include physical methods (e.g. adsorption [4], coagulation [5], biodegradation [6]) and chemical methods (e.g. chlorination, ozonation) etc [7]. Physical and biological methods do not destruct the pollutants but simply transfer the pollutant to another phase which again creates disposal problem. On the other hand chemical methods have the disadvantages of using strong oxidants like chlorine and ozone which are themselves hazardous in nature. However, photocatalytic technology as an advanced oxidation process (AOP) promotes the degradation of pollutants through producing hydroxyl radicals ( $\cdot\text{OH}$ ) from water molecules as strong oxidizing agent which eventually converts the organic dye molecules into  $\text{CO}_2$  gas.

The most important reason for choosing ZnO as photocatalyst is its ability to show photocatalytic efficiency in both UV and visible range of light i.e. direct sunlight can be used as light source. The focus of the present work is to synthesize ZnO nanoparticles and use it in the photocatalytic degradation of Brown CGG (sodium salt of 3-amino-4-7-hydroxy benzene sulfonic acid diazo, Fig. 1.), using sunlight illumination.

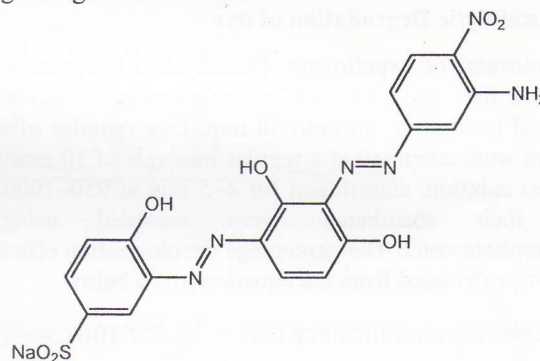


Fig. 1: Chemical structure of Brown CGG.

### 2. Experimental

#### Materials

Zinc nitrate hexahydrate [ $Zn(NO_3)_2 \cdot 6H_2O$ ] was purchased from JHD group, Guandong, China. Sodium hydroxide (NaOH) was obtained from NEN Tech. Ltd. Brixworth, UK. Brown CGG dye (molecular formula:  $C_{18}H_{13}N_6NaO_8S$ , formula weight: 496.39, C.I. No: 20250) was supplied by Apex Tannery Ltd, Hazaribag, Bangladesh. Stock solution of Brown CGG dye ( $2.5 \times 10^{-5} \text{ mol} \cdot \text{L}^{-1}$ ) was prepared daily by dissolving appropriate amount of dye solid in deionized water. All experiments were performed with analytical grade reagents and directly used without further purification. Doubly deionized water was used throughout.



### Apparatus

Ultraviolet visible (UV-vis) spectral measurements were performed on a UV-1700 (Shimadzu, Japan) spectrophotometer. ZnO crystal structures were characterized by X-ray diffractometry (XRD) using a D8 ADVANCE diffractometer (Bruker, Germany). The morphology and chemical composition of the ZnO nanoparticles were observed by means of JSM-6490 scanning electron microscopy (SEM) and EDX analysis (JEOL, USA). FTIR spectra were recorded on a Prestidge-21 IR (Shimadzu, Japan) spectrophotometer from samples in KBr pellets.

### Nanoparticle Preparation

ZnO nanoparticles were prepared following the procedure described elsewhere [8]. A 0.2 M solution of zinc nitrate and a 4.0 M alkali solution of sodium hydroxide were separately prepared by dissolving zinc nitrate hexahydrate  $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  and NaOH, respectively, in deionized water. To prepare ZnO nanoparticles, 2 mL of the alkali solution (4.0 M NaOH) was dropped at an approximate rate of 0.5 ml/min into a 20 mL aqueous solution of 0.2 M  $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  with stirring. The final pH of the mixture was fixed at 13 as highly basic conditions are conducive to the direct preparation of ZnO crystals [9]. The products obtained by centrifugation were washed with deionized water and dried at 60°C in air. Prepared ZnO was then characterized by UV, FTIR, EDX, XRD and SEM analysis.

### Photocatalytic Degradation of dye

In photocatalytic experiments, Brown CGG dye solution (50 ml) and the catalyst (ZnO), were taken in a beaker and exposed to sunlight for upto 40 min. Dye samples of about 2–3 ml were taken out at a regular intervals of 10 min from the test solution, centrifuged for 4–5 min at 950–1000 rpm and their absorbance were recorded using a spectrophotometer. The percentage decolorization efficiency (%) was calculated from the equation given below

$$\text{Decolorization Efficiency (\%)} = \frac{C_0 - C}{C_0} \times 100 \quad \text{--- (1)}$$

where  $C_0$  is the initial concentration of dye and  $C$  is the concentration of dye after photo irradiation at varying reaction time (expressed in  $\text{mol} \cdot \text{L}^{-1}$ ).

### Effluent Treatment

Colored effluent containing Brown CGG dye as a major constituent along with other dyes and dyeing auxiliaries was collected from the discharge line of a local leather processing plant (Apex Tannery Ltd, Hazaribag). The effluent was treated using the prepared ZnO nano under varying conditions. The same photocatalytic experimental set up, as used for the dye solution, was employed here for effluent treatment. The chemical oxygen demand (COD) of the untreated and treated (with ZnO nanoparticles) effluents was estimated using  $\text{KMnO}_4$  oxidation method [10].

## 3. Results and Discussion

### Analysis of ZnO Nanoparticle

A characteristic peak for ZnO nanoparticle was found in 350 nm wavelength in UV analysis (Figure 2a). Figure 2b shows the FT-IR spectra of the synthesized ZnO particles. The IR spectra of samples of ZnO particles are generally influenced by the particle size and morphology [9]. The peaks at wave number 671 and 559  $\text{cm}^{-1}$  are related to the stretching vibrations of Zn–O bonds. The peak at 3414  $\text{cm}^{-1}$  indicates the presence of –OH residue, probably due to atmospheric moisture [9]. The comparison of the synthesized ZnO peak in various plane with the JCPDS (Joint Committee on Powder Diffraction Standards) data shows presence of peak in similar position (Figure 2c). In case of synthesized ZnO, broad peaks of higher intensity affirm the smaller particle size [9, 11]. The crystallite size was calculated using Scherrer's formula [12] was found to be 18.79 nm. The SEM (Figure 2d) shows that the particles are uniform in shape and well dispersed with particle size below 200 nm. The chemical stoichiometry of ZnO nanoparticle was investigated with EDX (Figure 2e), which affirmed an atomic ratio of Zn:O = 48.02 : 51.98  $\approx$  1:1. No characteristic peaks of any other phase of ZnO or of any impurity were observed in XRD or EDX analysis. This result indicates the high purity of the ZnO nanoparticles.

### Photodegradation Studies

The UV spectral characteristics of the Brown CGG dye at different time intervals are shown in Figure 3. The dye was irradiated under sunlight in a 10 minutes interval for 40 minutes to observe if there is any degradation effect. The absorption peak gradually decreases as the concentration decreased. This is in agreement with the knowledge that the amount of organic compound contained is less for solution with lower concentration. The decreasing of the absorption peak at 440 nm indicates that the decomposition of organic compound in the solution has taken place. The effect of initial dye concentration on the decolorization efficiency was studied by varying the concentration from  $5 \times 10^{-5}$   $\text{mol} \cdot \text{L}^{-1}$  to  $2.5 \times 10^{-6}$   $\text{mol} \cdot \text{L}^{-1}$  and keeping ZnO (0.5 g·L<sup>-1</sup>) as constant. The results are presented in Figure 4. It is seen that the decolorization efficiency of Brown CGG dye decreases with the increase of initial dye concentrations. This follows from the fact that the active surface on the catalyst available for reaction is very crucial for the degradation to take place. As the dye concentration is increased and the catalyst amount is kept constant, this results in fewer active sites for the reaction. The rate constant (K) and  $t_{1/2}$  values for experimental values of different concentrations of Brown CGG dye are summarized in Table 1. It is observed that as the initial concentration decreases the rate constant increases and half life decreases. This means that the reaction became faster and more feasible with the decrease in concentration.



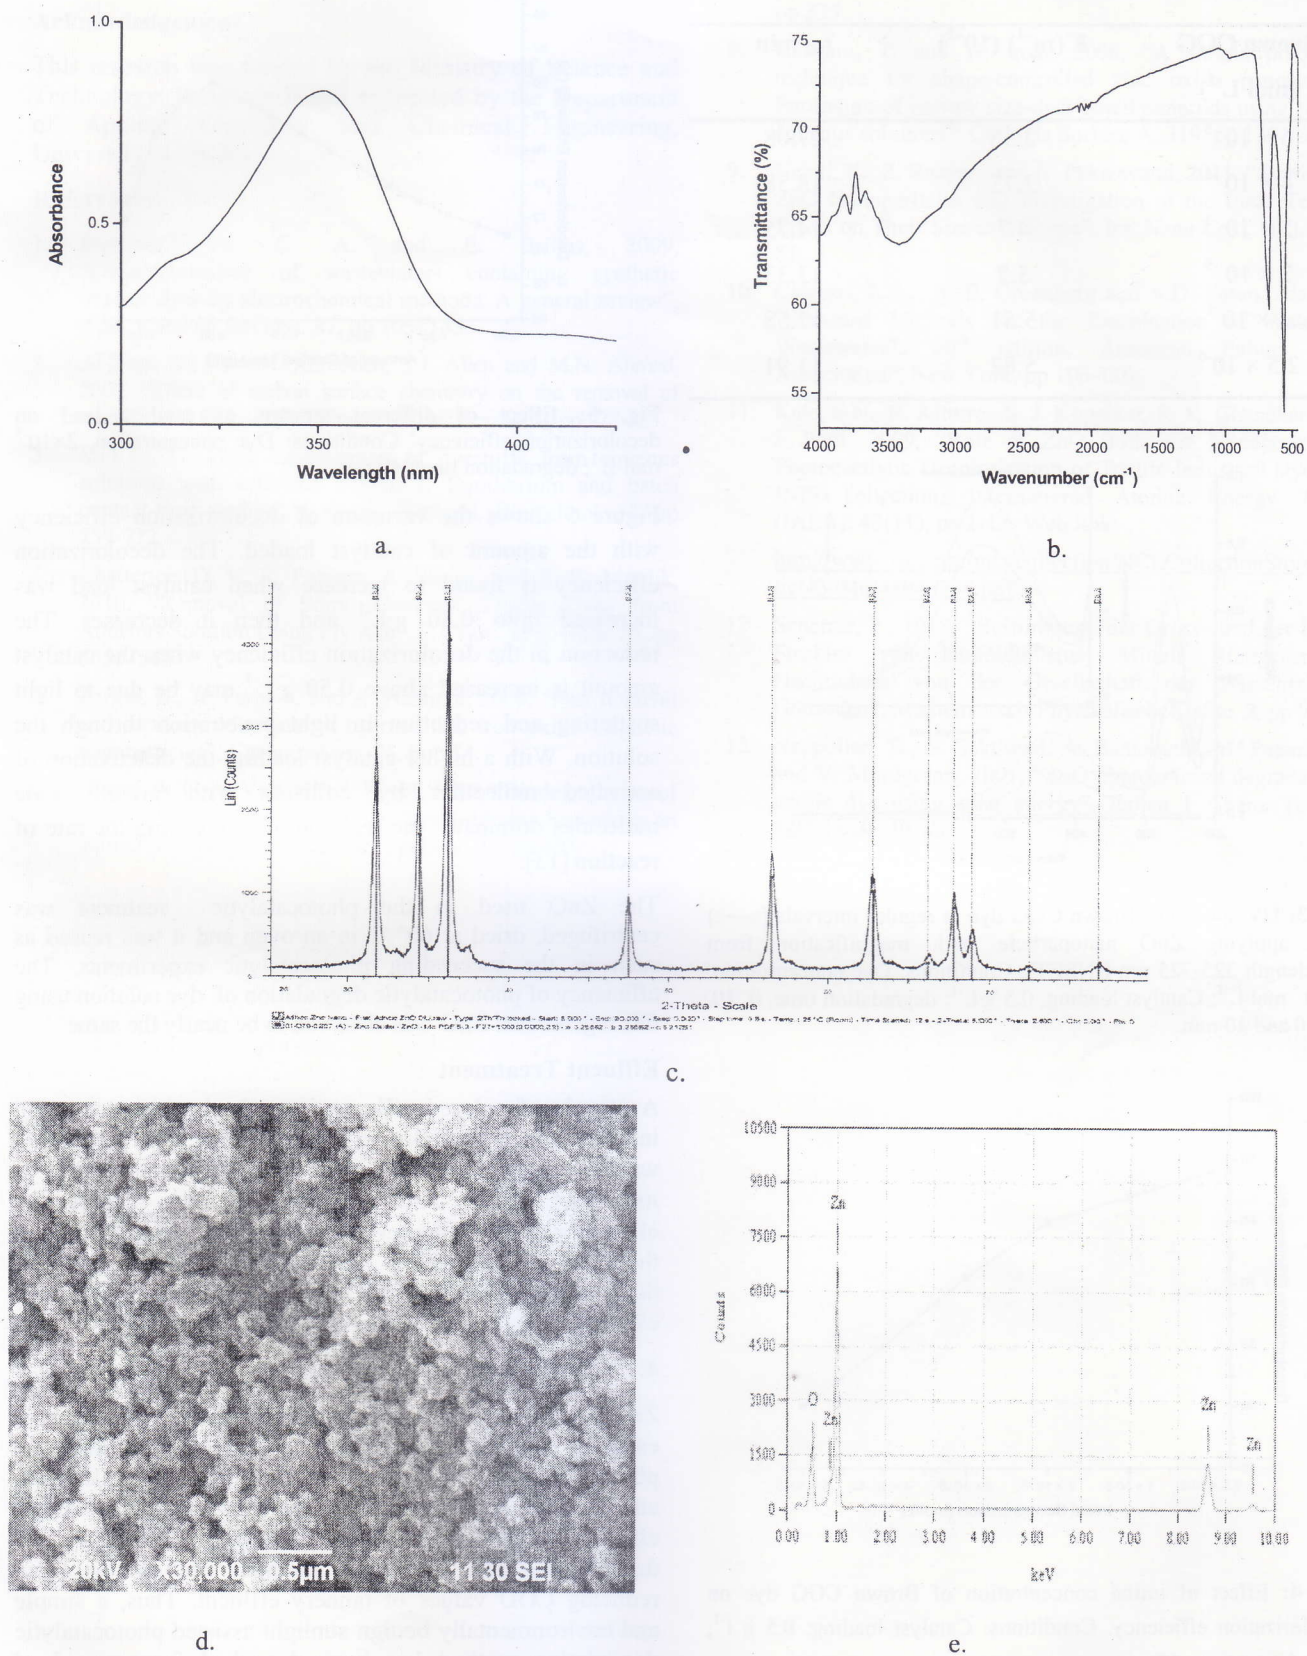


Fig. 2: Characteristics of prepared ZnO nanoparticle. a. UV-Visible; b. FT-IR; c. XRD d. SEM and e.EDX spectrum

**Table 1:** Rate constant and half life of degradation reaction for various initial concentrations

Brown CGG (mol·L <sup>-1</sup> )	<i>K</i> (m <sup>-1</sup> ) (10 <sup>-2</sup> )	<i>t</i> <sub>1/2</sub> min
5 × 10 <sup>-5</sup>	2.56	27.08
4 × 10 <sup>-5</sup>	3.73	18.58
3 × 10 <sup>-5</sup>	4.7	14.75
2 × 10 <sup>-5</sup>	5.2	13.33
1 × 10 <sup>-5</sup>	5.51	12.58
2.5 × 10 <sup>-6</sup>	5.82	11.91

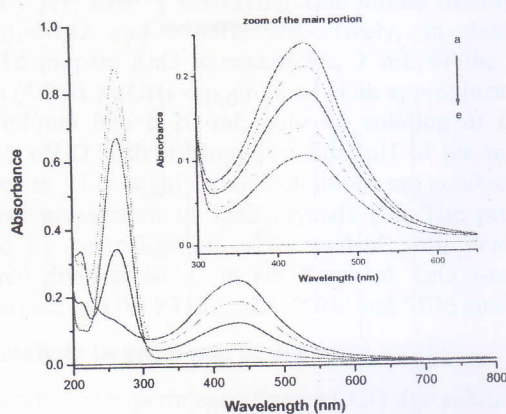
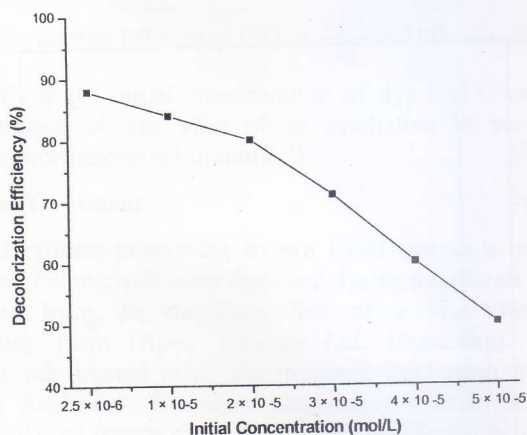
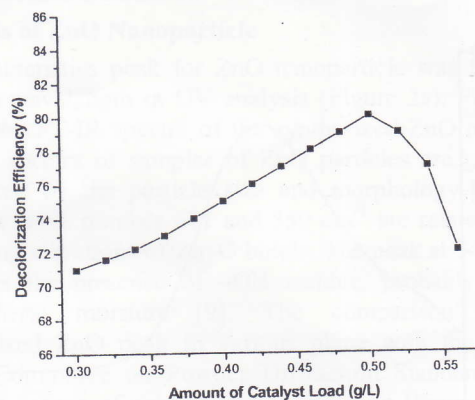
**Fig. 3:** UV spectra of Brown CGG dye at regular intervals (a→e) after applying ZnO nanoparticle with magnification from wavelength 325-725 nm (INSET). Conditions: Dye concentration, 2 × 10<sup>-5</sup> mol·L<sup>-1</sup>; Catalyst loading, 0.5 g·L<sup>-1</sup>; degradation time, 0, 10, 20, 30 and 40 min.**Fig. 4:** Effect of initial concentration of Brown CGG dye on decolorization efficiency. Conditions: Catalyst loading, 0.5 g l<sup>-1</sup>; degradation time, 40 min.**Fig. 5:** Effect of different amount of catalyst load on decolorization efficiency. Conditions: Dye concentration, 2 × 10<sup>-5</sup> mol·L<sup>-1</sup>; degradation time, 40 min.

Figure 5 shows the variation of decolorization efficiency with the amount of catalyst loaded. The decolorization efficiency is found to increase when catalyst load was increased upto 0.50 g·L<sup>-1</sup> and then it decreases. The reduction in the decolorization efficiency when the catalyst amount is increased above 0.50 g·L<sup>-1</sup> may be due to light scattering and reduction in light penetration through the solution. With a higher catalyst loading the deactivation of activated molecules by collision with ground state molecules dominates the reaction, thus reducing the rate of reaction [13].

The ZnO used in the photocatalytic treatment was centrifuged, dried at 60° C in an oven and it was reused as such in the succeeding photocatalytic experiments. The efficiency of photocatalytic degradation of dye solution using this regenerated ZnO was observed to be nearly the same.

#### Effluent Treatment

A sample of colored effluent from the leather processing industry which uses Brown CGG dye and other chemicals was subjected to the photocatalytic degradation of dye molecules using ZnO nanoparticle. The degradation efficiency of the effluent was evaluated in this study through the COD of the treated and untreated effluent. Thus the degradation efficiency of the effluent under the given experimental conditions was obtained as 72.86%.

#### 4. Conclusion

ZnO nanoparticle was successfully prepared with a cheap, easy to operate and reproducible procedure and the physicochemical properties of ZnO nano crystals were analyzed. The prepared ZnO nanoparticle photocatalyst effectively treated Brown CGG dye leading to its degradation. The developed method was successful in reducing COD values of tannery effluent. Thus, a simple and environmentally benign sunlight assisted photocatalytic degradation method has been described for removal of



Brown CGG, a common dye used in tannery industries of Bangladesh.

#### Acknowledgement

This research was funded by the Ministry of Science and Technology, Bangladesh and supported by the Department of Applied Chemistry and Chemical Engineering, University of Dhaka.

#### References

1. Martinez-Huitle, C. A. and E. Brillas, 2009, "Decontamination of wastewaters containing synthetic organic dyes by electrochemical methods: A general review", *Appl. Catal. B: Environ.* 87, pp 105-145.
2. Al-Degs, Y., M.A.M. Khraisheh, S.J. Allen and M.N. Ahmad, 2000, "Effect of carbon surface chemistry on the removal of reactive dyes from textile effluent", *Water Res.* 34(3), pp 927-935.
3. McKay, G. 1982, "Adsorption of dyestuffs from aqueous solutions with activated carbon I: Equilibrium and batch contact-time studies", *J. Chem. Technol. Biotechnol.* 32, pp 759-772.
4. Chatterjee, D. V. R. Patnam, A. Sikdar, and S. K. Moulik, 2010, "Removal of Some Common Textile Dyes from Aqueous Solution Using Fly Ash", *J. Chem. Eng. Data*, 55, pp 5653-5657.
5. Zargar, B., H. Parham, and A. Hatamie, 2009, "Fast removal and recovery of amaranth by modified iron oxide magnetic nanoparticles", *Chemosphere*, 76, pp 554.
6. Moore, A.T., A. Vira, and S. Fogel, 1989, "Biodegradation of trans-1,2-dichloroethylene by methane-utilizing bacteria in an aquifer simulator", *Environ Sci Technol*, 23, pp 403.
7. Slokar, Y.M. and A.M. Le Marechal, 1998, "Methods of decoloration of textile wastewaters", *Dyes Pigments*, 37(4), pp 335.
8. Kawano, T. and H. Imai, 2008, "A simple preparation technique for shape-controlled zinc oxide nanoparticles: Formation of narrow size-distributed nanorods using seeds in aqueous solutions", *Colloids Surface A*. 319, pp 130-135.
9. Nejati, K., Z. Rezvani and R. Pakizevand, 2011, "Synthesis of ZnO Nanoparticles and Investigation of the Ionic Template Effect on Their Size and Shape", *Int. Nano Lett.*, 1(2), pp 75-81.
10. Clesceri, L.S., A. E. Greenberg and A.D. Eaton, eds. 1998, "Standard Methods for the Examination of Water and Wastewater", 20<sup>th</sup> edition, American Public Health Association", New York, pp 106-110.
11. Kale, S.N., R. Kitture, S. J. Koppikar, R. K. Ghanekar and S. I. Patil, 2009, "Role of ZnO Bulk and Nanopowders in Photocatalytic Decolorisation of Textile Industrial Dyes", In: INIS collection, International Atomic Energy Agency (IAEA), 43(11), pp 1-13. Web link: <http://www.iaea.org/inis/collection/NCLCollectionStore/Public/43/046/43046234.pdf>
12. Scherrer, P., 1918, "Bestimmung der Größe und der Inneren Struktur von Kolloidteilchen Mittels Röntgenstrahlen, Nachrichten von der Gesellschaft der Wissenschaften, Göttingen", *Mathematisch-Physikalische Klasse*, 2, pp 98-100.
13. Neppolian, B., S. Sakthivel, A. Banumathi, M. Palanichamy and V. Murugesan, 2001, "ZnO-photoassisted degradation of textile dye using solar energy", *Indian J. Chem. Technol.*, 8(1), pp 36-40.